



[UF₆]²⁻: A Molecular Hexafluorido Actinide(IV) Complex with Compensating Spin and Orbital Magnetic Moments

Kasper S. Pedersen,* Katie R. Meihaus, Andrei Rogalev,* Fabrice Wilhelm, Daniel Aravena, Martín Amoza, Eliseo Ruiz, Jeffrey R. Long, Jesper Bendix, and Rodolphe Clérac*

Abstract: The first structurally characterized hexafluorido complex of a tetravalent actinide ion, the [UF₆]²⁻ anion, is reported in the (NEt₄)₂[UF₆]·2H₂O salt (**1**). The weak magnetic response of **1** results from both U^{IV} spin and orbital contributions, as established by combining X-ray magnetic circular dichroism (XMCD) spectroscopy and bulk magnetization measurements. The spin and orbital moments are virtually identical in magnitude, but opposite in sign, resulting in an almost perfect cancellation, which is corroborated by ab initio calculations. This work constitutes the first experimental demonstration of a seemingly non-magnetic molecular actinide complex carrying sizable spin and orbital magnetic moments.

The chemistry of uranium compounds and the diversity of potential uses for uranium in novel materials are currently experiencing a renaissance.^[1] Molecular complexes with uranium in either + III or + V oxidation states have been shown to generally exhibit slow relaxation of magnetization,^[2] together with a single U^{IV} complex that appears as an exception.^[3] Such complexes are also interesting building blocks for magnetic polynuclear complexes and one-dimensional coordination polymers.^[4] Recent spectroscopic and theoretical investigations have aimed at a detailed understanding of the electronic structure of actinide ions, which is significantly more complicated than for lanthanides.^[5] The large spin-orbit coupling of actinide ions and the less shielded nature of their 5f orbitals relative to the 4f orbitals, result in much stronger interactions of the f electrons with the

surrounding atoms. Hence, the concomitant stronger ligand field cannot be considered as a perturbation, particularly for the early members of the 5f series. Furthermore, spectroscopic data of actinide systems are typically very rich and the determination of the electronic energy level-splitting and -composition remains quite challenging. For the magnetic characterization of actinide-based materials, powder and thermodynamically averaged magnetization data bring only limited information about the underlying physics. However, since the magnetic properties are predominantly defined by the energy levels that are thermally populated at room temperature and below, any additional experimental information on these low-lying energy levels would be of great relevance. For this task, X-ray magnetic circular dichroism spectroscopy is a powerful tool able to deconvolute the macroscopically measured magnetic moment into its spin and orbital contributions.^[6] Despite its routine applications in magnetism, this technique has never been applied to molecular actinide systems.^[7] Inspired by the early works of Ryan et al. and Brown et al.,^[8a,b] we herein report the synthesis and crystal structure of (NEt₄)₂[UF₆]·2H₂O (**1**) featuring the first structurally characterized example of an octahedral fluoride complex in the tetravalent actinide family.^[8] Although the octahedral [UF₆] and [UF₆]⁻ complexes have been well-described and structurally characterized,^[9] the existence of an octahedral [UF₆]²⁻ has only been inferred from vibrational spectroscopy, but not confirmed by X-ray crystallography.^[8a,b] Indeed, more generally, despite the vast number of known fluoride complexes and solids of the actinide ions, no

[*] Prof. Dr. K. S. Pedersen, Dr. R. Clérac
Univ. Bordeaux, CNRS, Centre de Recherche Paul Pascal, UMR 5031
33600 Pessac (France)
E-mail: cleric@crpp-bordeaux.cnrs.fr
Prof. Dr. K. S. Pedersen
Department of Chemistry, Technical University of Denmark
2800 Kgs. Lyngby (Denmark)
E-mail: kastp@kemi.dtu.dk
Dr. K. R. Meihaus, Prof. Dr. J. R. Long
Department of Chemistry, University of California
Berkeley, CA 94720 (USA)
Dr. A. Rogalev, Dr. F. Wilhelm
ESRF-The European Synchrotron
71, Avenue des Martyrs, 38000 Grenoble Cedex 9 (France)
E-mail: rogalev@esrf.fr
Dr. D. Aravena
Departamento de Química de los Materiales
Facultad de Química y Biología
Universidad de Santiago de Chile (USACH)
Casilla 40, Correo 33, Santiago (Chile)

M. Amoza, Prof. Dr. E. Ruiz
Departament de Química Inorgànica i Orgànica and Institut de
Química Teòrica i Computacional, Universitat de Barcelona
Diagonal 645, 08028 Barcelona (Spain)
Prof. Dr. J. R. Long
Materials Sciences Division, Lawrence Berkeley National Laboratory
Berkeley, CA 94720 (USA),
and
Department of Chemical and Biomolecular Engineering
University of California Berkeley
Berkeley, CA 94720 (USA)
Prof. Dr. J. Bendix
Department of Chemistry, University of Copenhagen
2100 Copenhagen (Denmark)
 Supporting information and the ORCID identification number(s) for
 the author(s) of this article can be found under:
<https://doi.org/10.1002/anie.201905056>.

hexafluoride complex of the tetravalent actinides has yet been structurally characterized.

The reaction of $\text{UF}_4 \cdot x \text{H}_2\text{O}$ ($x \approx 1.5$) with $\text{NEt}_4\text{F} \cdot \text{H}_2\text{O}$ in propylene carbonate under a dry N_2 atmosphere yields a pale green solution. Addition of acetone induces the crystallization of a pale-green material suitable for single-crystal X-ray diffraction. The crystal structure analysis of $(\text{NEt}_4)_2 \cdot [\text{UF}_6] \cdot 2\text{H}_2\text{O}$ (**1**) reveals the presence of slightly compressed octahedral $[\text{UF}_6]^{2-}$ complexes (Figure 1), with U–F bond

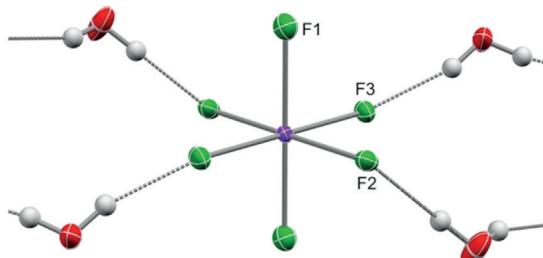


Figure 1. Molecular structure of the $[\text{UF}_6]^{2-}$ complex in **1** (ellipsoids set at 50% probability) and the hydrogen bonding pattern linking $[\text{UF}_6]^{2-}$ complexes into supramolecular chains running along the crystallographic *c* direction (Supporting Information, Figure S1).^[28] Selected bond lengths [\AA] and angles [$^\circ$]: U–F1 2.124(2), U–F2 2.177(2), U–F3 2.181(2), *cis*-F–U–F 89.23(7)–90.90(7). U purple, F green, O red, C black, H gray.

lengths being longer for fluoride ligands engaged in hydrogen bonding (2.177(2) and 2.181(2) \AA versus 2.124(2) \AA ; Supporting Information, Figure S1). The U–F bond lengths are also significantly longer than those found in $[\text{UF}_6]^-$ (av. U–F 2.07 \AA) and $[\text{UF}_6]$ (av. U–F 1.98 \AA),^[10] but comparable to those of organometallic U^{IV} complexes such as $[\text{Cp}^*_2\text{UF}_2(\text{py})]$ (Cp^* = pentamethylcyclopentadienide, py = pyridine; av. U–F 2.15 \AA) and $[\text{Cp}_3\text{UF}]$ (Cp = cyclopentadienide; U–F 2.11 \AA).^[11]

The temperature dependence of the magnetic susceptibility–temperature product, χT , of **1** is shown in Figure 2a. From $0.35 \text{ cm}^3 \text{K mol}^{-1}$ at 300 K, it nearly vanishes to $5 \times 10^{-3} \text{ cm}^3 \text{K mol}^{-1}$ at 1.8 K, which is far from the $1.60 \text{ cm}^3 \text{K mol}^{-1}$ value expected for the Russell–Saunders atomic ground state term of the 5f^2 configuration (${}^3\text{H}_4$, $g_J=4/5$).^[12] The electronic ground state of U^{IV} in octahedral symmetry is a singlet state composed of a linear combination of the $|m_J=0\rangle$ and $|m_J=\pm 1\rangle$ states.^[13] Thus, the magnetic susceptibility is expected to be dominated by temperature-independent paramagnetism (TIP). The simulated χT product, using the model developed in reference [13] with our ab initio results (see below), is shown in Figure 2a. The experimental departure from the idealized TIP dependence differs from the behavior of $[\text{UCl}_6]^{2-}$ and $[\text{UBr}_6]^{2-}$ analogues,^[14] but is nevertheless commonly observed for U^{IV} systems.^[12] To obtain experimental information on the nature of the electronic ground state of uranium in **1**, X-ray absorption spectroscopy (XAS) and X-ray magnetic circular dichroism (XMCD) were employed.

The uranium $M_{4,5}$ XAS spectra are dominated by strong resonance lines, so-called white lines, that are due to dipole-

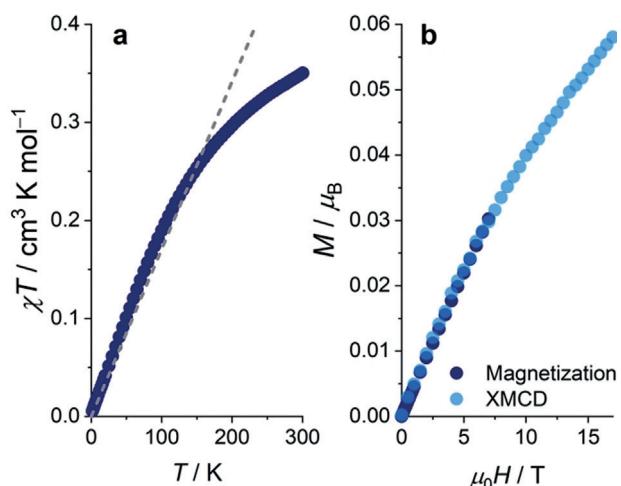


Figure 2. a) Temperature dependence of the χT product (χ being the magnetic susceptibility defined as $M/\mu_0 H$) over the 1.8–300 K range (0.3 K min^{-1}) of a polycrystalline sample of **1** obtained with $\mu_0 H=1.0$ T. The gray dashed line is the calculated χT product using the model of Ref. [13] with a Γ_1 – Γ_4 energy splitting of 1300 cm^{-1} . b) Field-dependence of the magnetization, $M(\mu_0 H)$, obtained at 4 K in the 0–7 T range and the scaled field dependence of the XMCD signal measured in the 0–17 T range at a photon energy of 3727.3 eV corresponding to the maximum of the XMCD signal at the uranium M_4 edge.

allowed transitions from the spin-orbit split $3d_{3/2,5/2}$ levels into the magnetic 5f states along with much weaker $3d \rightarrow 6p$ and $3d \rightarrow$ continuum transitions. According to the dipole selection rule ($\Delta J=\pm 1$), the larger M_5 white line intensity primarily reflects the population of the $5f_{7/2}$ states and the weaker M_4 intensity only the $5f_{5/2}$ states.^[15] In Figure 3a, the XAS $M_{4,5}$ spectra are shown on the same relative energy scale that is obtained by shifting the original spectra (Figure 3b, gray trace) to perfectly overlap the first EXAFS oscillation (inset Figure 3a). It is apparent, that the absorption maxima of the M_5 and M_4 white lines are at different photon energies separated by about 0.8 eV, with the M_4 peak being at lower photon energies. This energy splitting is due to spin-orbit coupling of the 5f states. In a spherically symmetric ligand field, the magnitude of this gap can be approximated by $\Delta E = \gamma_2 \xi_{5f}$, where ξ_{5f} is the spin-orbit parameter for the 5f electrons. The angular part of the spin-orbit interaction for the 5f states, $\langle \sum_i \mathbf{l}_i \cdot \mathbf{s}_i \rangle$, can be obtained using the so-called spin-orbit sum rule, which relates its ground-state expectation value to the branching ratio (BR) of the isotropic X-ray absorption intensities.^[16] The experimental BR value, 0.727 ± 0.005 , of **1** results in $\langle \sum_i \mathbf{l}_i \cdot \mathbf{s}_i \rangle/h^2 \approx -5.7$, which is significantly larger than the values obtained by atomic calculations on the 5f^2 configuration of –3, –4, and –3.88 in the Russell–Saunders, $j-j$, and intermediate coupling scheme, respectively.^[17] It should be noted that the spin-orbit sum rule has been derived neglecting the core-valence interaction. The observed deviation from theory is thus not unexpected because of the highly localized nature of the 5f states in **1**, where core-valence interaction could be very strong. Indeed, such discrepancies with theoretical models have already been

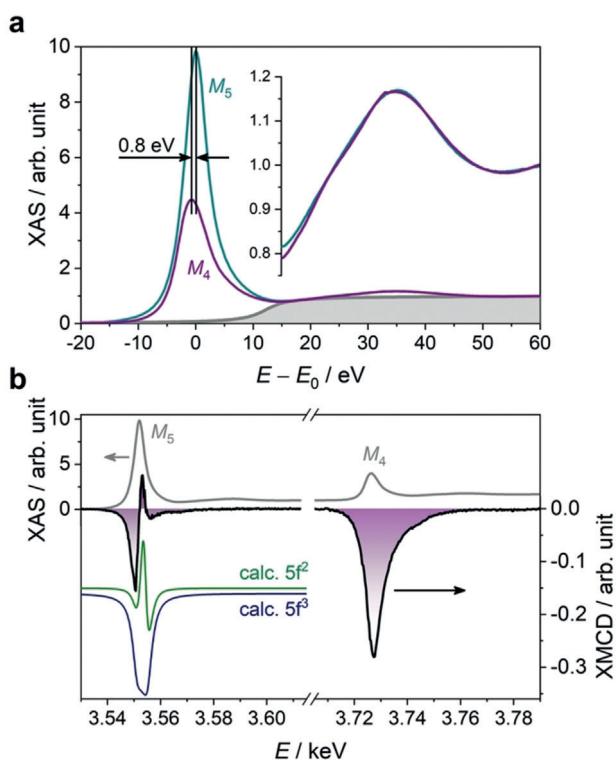


Figure 3. a) Isotropic XAS spectra of **1** obtained at the uranium M_5 and M_4 edges shown on the same relative energy scale (see the Supporting Information). The gray line represents the step function mimicking transitions into continuum. The inset is a magnification of the first EXAFS oscillation used to determine the relative energy scale. b) Isotropic XAS (gray lines) and XMCD (black lines) spectra of **1** obtained at the M_5 and M_4 edges in a magnetic field of 17 T at 4 K. The filled patterns indicate the integrals employed for the magneto-optical sum rules analysis. The theoretical XMCD spectra for both the $5f^2$ (green trace) and $5f^3$ (blue trace) configurations were obtained from multiplet calculations employing the ligand field parameters extracted from ab initio calculations (see text and Supporting Information, Figures S2, S3).

observed in electron energy loss spectroscopy results obtained on various U^{IV} oxide minerals.^[18]

The normalized XMCD spectra at the uranium $M_{4,5}$ edges are shown on Figure 3b. Sizeable dichroism signals are observed at both M_4 and M_5 edges. The spectral shape of the XMCD at the M_5 edge is in qualitative agreement with the one estimated from multiplet calculations for the $5f^2$ configuration with an octahedral ligand field (Figure 3b, green trace), and with experimental results on U^{IV} -containing metals.^[15] This favorable comparison of the uranium M_5 XMCD spectral shape, which is extremely sensitive to the $5f$ occupation, confirms also the $5f^2$ configuration of uranium in **1**. To deduce the magnitudes of the magnetic moments carried by the uranium $5f$ states, the so-called magneto-optical sum rules can be used, which relate the integrals of the XMCD spectra to the orbital (orbital sum rule)^[19] and spin (spin sum rule)^[20] magnetic moments. Unfortunately, the spin sum rule is based on the same approximation as the spin-orbit sum rule, and can therefore hardly be applied to our XMCD spectra. Nevertheless, the orbital sum rule remains valid irrespective of this approximation and numerical integration

of the XMCD spectra shown in Figure 3b affords $M_{\text{orbital}} = 0.47 \mu_B$. The spin moment, M_{spin} , may hereafter be determined by scaling the magnetization curve measured by monitoring the M_4 XMCD signal as a function of the applied magnetic field (shown in Figure 2b) to the macroscopic magnetization data. This procedure allows the estimation of the absolute magnetization at 17 T, which amounts to only $M_{\text{total}} = 0.060 - (4) \mu_B$ thereby yielding $M_{\text{spin}} = -0.41 \mu_B$ through the $M_{\text{total}} = M_{\text{orbital}} + M_{\text{spin}}$ relation. Thus, the analysis of the XMCD spectra reveals, unambiguously, the existence of sizable orbital and spin magnetic moments in **1** despite a low bulk magnetic moment. Similar cancellation of spin and orbital magnetizations for uranium has already been observed in itinerant 5f systems like UFe_2 using neutron scattering and confirmed by XMCD.^[21] Here, we demonstrate that the spin-orbital cancellation is not limited to metallic systems with strongly delocalized 5f states but is also present in a molecular system with much higher degree of 5f localization.

Ab initio CASSCF^[22] and NEVPT2^[23] calculations on the $[\text{UF}_6]^{2-}$ complex predict significantly lower orbital and spin magnetic moments of the ground state ($M_{\text{orbital}} = -0.051 \mu_B$ and $M_{\text{spin}} = 0.018 \mu_B$, NEVPT2). Considering the idealized high-symmetry environment of the $[\text{UF}_6]^{2-}$ moiety, it is reasonable to explore the influence of vibronic effects on the magnetic properties of the complex. The calculations indicate that the A_{1g} ground state is separated from the excited states by more than 1000 cm^{-1} for both the crystal structure model and an idealized octahedral geometry. Thus, there is no ground state degeneracy and vibronic effects must be related to a pseudo-Jahn-Teller mechanism.^[24] To evaluate if vibronic coupling impacts the magnetic moments, a Hamiltonian was built with diagonal elements corresponding to state energies including spin-orbit effects and a Zeeman term. The state interaction between the ground state, 0, and an excited state, a , is represented by the following expression [Eq. (1)]:

$$\mathcal{H}_{0a} = -\mu_B \mu_0 (g_e \mathbf{S}_{0a} + \mathbf{L}_{0a}) \cdot \mathbf{H} + F_{0a} \lambda \quad (1)$$

where $S_{0a,i} = \langle \Psi_a | \hat{S}_i | \Psi_0 \rangle$ and $L_{0a,i} = \langle \Psi_a | \hat{L}_i | \Psi_0 \rangle$ for $i = x, y$, and z . The first term corresponds to the Zeeman interaction and the second is the linear vibronic contribution with coupling constants [Eq. (2)]:

$$F_{0a} = \langle \Psi_a | \frac{d\hat{\mathcal{H}}_0}{d\lambda} | \Psi_0 \rangle \quad (2)$$

where \mathcal{H}_0 is evaluated considering the crystallographically determined geometry, and Ψ_0 and Ψ_a are ground and excited state wave functions, respectively (see Supporting Information for further details). Vibronic mixing quickly increases the magnetic moment and then stabilizes for low displacement values (ca. $\lambda = 0.03 \text{ \AA}$; Supporting Information, Figure S5). If we consider 0.03 \AA as a representative displacement, we obtain $M_{\text{orbital}} = 0.48 \mu_B$ and $M_{\text{spin}} = -0.26 \mu_B$, which are in reasonable agreement with the experiment. Thus, the influence of the vibronic couplings on the magnetic properties is remarkably important for the $[\text{UF}_6]^{2-}$ complex, but there are no reasons to believe that this effect is restricted to this

particular system. Indeed, the magnitude of the magnetic moment in UO_2 could only be explained by invoking dynamic Jahn-Teller couplings,^[25] and the inelastic neutron scattering spectra of the lowest-lying crystal field states of UF_4 and UCl_4 have revealed the signatures of strong couplings between electronic states and vibrations.^[26]

In conclusion, this work reports on the $[\text{UF}_6]^{2-}$ complex, which is the first example of a structurally characterized hexafluorido actinide(IV) complex. Despite the very weak total magnetic moment of $[\text{UF}_6]^{2-}$, the detailed study and analysis of its magnetic properties combining state-of-the-art X-ray absorption spectroscopy, magnetometry, and quantum chemical calculations have demonstrated the existence of relatively large spin and orbital magnetic moments. These moments are roughly one hundred times larger than those found in related 5d systems with electronic singlet ground states.^[27] These significant spin and orbital components should be considered in the future analyses of the magnetic exchange interactions in uranium(IV)-based materials and fuel the curiosity for a fundamental understanding of the electronic structure and magnetism of other actinide-containing molecules and materials.

Acknowledgements

K.S.P. and R.C. thank the Danish Research Council for Independent Research for a DFF-Sapere Aude Research Talent grant (4090-00201), the University of Bordeaux, the Region Nouvelle Aquitaine, the CNRS, the GdR MCM-2 and the MOLSPIN COST action CA15128. R.C. and J.R.L. are grateful to the France-Berkeley Fund and the CNRS (PICS No. 06485) for funding. Research at the University of California, Berkeley was supported by NSF Grant CHE-1800252 to K.R.M. and J.R.L.. D.A. thanks FONDECYT Regular 1170524 project for financial support. Powered@NLHPC: This research was partially supported by the supercomputing infrastructure of the NLHPC (ECM-02). M.A. and E.R. thank Ministerio de Economía y Competitividad for grant PGC2018-093863-B-C21 and for computacional resources to CSUC. M.A. acknowledges the Ministerio de Educación y Formación Profesional for a FPU predoctoral grant. E.R. thanks Generalitat de Catalunya for an ICREA Academia grant. The X-ray spectroscopy experiments were performed at the ID12 beamline of the European Synchrotron Radiation Facility (ESRF, Grenoble, France). The authors thank warmly Patricia Verdugo for creating an image for consideration for the front cover.

Conflict of interest

The authors declare no conflict of interest.

Keywords: electronic structure · fluorides · magnetic properties · uranium · X-ray spectroscopy

How to cite: *Angew. Chem. Int. Ed.* **2019**, *58*, 15650–15654
Angew. Chem. **2019**, *131*, 15797–15801

- [1] S. T. Liddle, *Angew. Chem. Int. Ed.* **2015**, *54*, 8604; *Angew. Chem.* **2015**, *127*, 8726.
- [2] a) J. D. Rinehart, J. R. Long, *J. Am. Chem. Soc.* **2009**, *131*, 12558; b) J. D. Rinehart, K. R. Meihaus, J. R. Long, *J. Am. Chem. Soc.* **2010**, *132*, 7572; c) D. P. Mills, F. Moro, J. McMaster, J. van Slageren, W. Lewis, A. J. Blake, S. T. Liddle, *Nat. Chem.* **2011**, *3*, 454; d) F. Moro, D. Mills, S. T. Liddle, J. van Slageren, *Angew. Chem. Int. Ed.* **2013**, *52*, 3430; *Angew. Chem.* **2013**, *125*, 3514; e) K. R. Meihaus, S. G. Minasian, W. W. Lukens, S. A. Kozimor, D. K. Shuh, T. Tyliszczak, J. R. Long, *J. Am. Chem. Soc.* **2014**, *136*, 6056; f) K. R. Meihaus, J. R. Long, *J. Am. Chem. Soc.* **2015**, *137*, 2517; g) D. M. King, F. Tuna, J. McMaster, W. Lewis, A. J. Blake, E. J. L. McInnes, S. T. Liddle, *Angew. Chem. Int. Ed.* **2013**, *52*, 4921; *Angew. Chem.* **2013**, *125*, 5021.
- [3] M. A. Antunes, J. T. Coutinho, I. C. Santos, J. Marcalo, M. Almeida, J. J. Baldovi, L. C. J. Pereira, A. Gaita-Arino, E. Coronado, *Chem. Eur. J.* **2015**, *21*, 17817.
- [4] a) V. Mougel, L. Chatelain, J. Pécaut, R. Caciuffo, E. Colineau, J.-C. Griveau, M. Mazzanti, *Nat. Chem.* **2012**, *4*, 1011; b) V. Mougel, L. Chatelain, J. Hermle, R. Caciuffo, E. Colineau, F. Tuna, N. Magnani, A. De Geyer, J. Pécaut, M. Mazzanti, *Angew. Chem. Int. Ed.* **2014**, *53*, 819; *Angew. Chem.* **2014**, *126*, 838; c) L. Chatelain, J. P. S. Walsh, J. Pécaut, F. Tuna, M. Mazzanti, *Angew. Chem. Int. Ed.* **2014**, *53*, 13434; *Angew. Chem.* **2014**, *126*, 13652.
- [5] a) A. Formanuk, A.-M. Ariciu, F. Ortú, R. Beekmeyer, A. Kerridge, F. Tuna, E. J. L. McInnes, D. P. Mills, *Nat. Chem.* **2017**, *9*, 578; b) D. M. King, P. A. Cleaves, A. J. Woole, B. M. Gardner, N. F. Chilton, F. Tuna, W. Lewis, E. J. L. McInnes, S. T. Liddle, *Nat. Commun.* **2016**, *7*, 13773; c) M. Gregson, E. Lu, D. P. Mills, F. Tuna, E. J. L. McInnes, C. Hennig, A. C. Scheinst, J. McMaster, W. Lewis, A. J. Blake, A. Kerridge, S. T. Liddle, *Nat. Commun.* **2017**, *8*, 14137; d) A. Bronova, T. Droß, R. Glaum, H. Lueken, M. Speldrich, W. Urland, *Inorg. Chem.* **2016**, *55*, 6848; e) J. T. Coutinho, M. Perfetti, J. J. Baldoví, M. A. Antunes, P. P. Hallmen, H. Bamberger, I. Crassee, M. Orlita, M. Almeida, J. van Slageren, L. C. J. Pereira, *Chem. Eur. J.* **2019**, *25*, 1758; f) E. Lu, A. J. Woole, M. Gregson, P. J. Cobb, S. T. Liddle, *Angew. Chem. Int. Ed.* **2018**, *57*, 6587; *Angew. Chem.* **2018**, *130*, 6697.
- [6] G. van der Laan, A. I. Figueiroa, *Coord. Chem. Rev.* **2014**, *277*–278, 95.
- [7] a) S. P. Collins, D. Laundy, C. C. Tang, G. van der Laan, *J. Phys. Condens. Matter* **1995**, *7*, 9325; b) P. Dalmas de Reotier, J. P. Sanchez, A. Yaouanc, M. Finazzi, P. Sainctavit, P. Krill, J. P. Kappler, J. Goedkoop, J. Goulon, C. Goulon-Gibet, A. Rogalev, O. Vogt, *J. Phys. Condens. Matter* **1997**, *9*, 3291; c) F. Wilhelm, N. Jaouen, A. Rogalev, W. G. Stirling, R. Springell, S. W. Zochowski, A. M. Beesley, S. D. Brown, M. F. Thomas, G. H. Lander, S. Langridge, R. C. C. Ward, M. R. Wells, *Phys. Rev. B* **2007**, *76*, 024425; d) N. Magnani, R. Caciuffo, F. Wilhelm, E. Colineau, R. Eloirdi, J.-C. Griveau, J. Rusz, P. M. Oppeneer, A. Rogalev, G. H. Lander, *Phys. Rev. Lett.* **2015**, *114*, 097203; e) N. Magnani, R. Eloirdi, F. Wilhelm, E. Colineau, J. C. Griveau, A. B. Shick, G. H. Lander, A. Rogalev, R. Caciuffo, *Phys. Rev. Lett.* **2017**, *119*, 157204; f) F. Wilhelm, J. P. Sanchez, J. P. Brison, D. Aoki, A. B. Shick, A. Rogalev, *Phys. Rev. B* **2017**, *95*, 235147; g) F. Wilhelm, J. P. Sanchez, A. Rogalev, *J. Phys. D* **2018**, *51*, 333001.
- [8] a) J. L. Ryan, J. M. Cleveland, G. H. Bryan, *Inorg. Chem.* **1974**, *13*, 214; b) D. Brown, B. Whittaker, N. Edelstein, *Inorg. Chem.* **1974**, *13*, 1805; c) B. Ordejón, L. Seijo, Z. Barandiarán, *J. Chem. Phys.* **2005**, *123*, 204502; d) B. Ordejón, M. Karbowiak, L. Seijo, Z. Barandiarán, *J. Chem. Phys.* **2006**, *125*, 074511.
- [9] a) Y.-L. Lai, R.-K. Chiang, K.-H. Lii, S.-L. Wang, *Chem. Mater.* **2008**, *20*, 523; b) R. J. Francis, P. S. Halasyamani, J. S. Bee, D. O'Hare, *J. Am. Chem. Soc.* **1999**, *121*, 1609; c) B. Scheibe, S. Lippert, S. S. Rudel, M. R. Buchner, O. Burghaus, C. Peitzonka,

- M. Koch, A. J. Karttunen, F. Kraus, *Chem. Eur. J.* **2016**, 22, 12145.
- [10] a) M. P. Eastman, P. G. Eller, G. W. Halstead, *J. Inorg. Nucl. Chem.* **1981**, 43, 2839; b) C. G. Gianopoulos, V. V. Zhurov, S. G. Minasian, E. R. Batista, C. Jelsch, A. A. Pinkerton, *Inorg. Chem.* **2017**, 56, 1775; c) J. H. Levy, J. C. Taylor, P. W. Wilson, *J. Chem. Soc. Dalton Trans.* **1976**, 219.
- [11] a) R. K. Thomson, C. R. Graves, B. L. Scott, J. L. Kiplinger, *Dalton Trans.* **2010**, 39, 6826; b) R. R. Ryan, R. A. Penneman, B. Kanellakopulos, *J. Am. Chem. Soc.* **1975**, 97, 4258.
- [12] D. R. Kindra, W. J. Evans, *Chem. Rev.* **2014**, 114, 8865.
- [13] C. A. Hutchison, G. A. Candela, *J. Chem. Phys.* **1957**, 27, 707.
- [14] J. P. Day, L. M. Venanzi, *J. Chem. Soc. A* **1966**, 197.
- [15] a) A. Yaouanc, P. Dalmas de Réotier, G. van der Laan, A. Hiess, J. Goulon, C. Neumann, P. Lejay, N. Sato, *Phys. Rev. B* **1998**, 58, 8793; b) P. Dalmas de Réotier, A. Yaouanc, G. van der Laan, N. Kernavanois, J.-P. Sanchez, J. L. Smith, A. Hiess, A. Huxley, A. Rogalev, *Phys. Rev. B* **1999**, 60, 10606; c) V. N. Antonov, B. N. Harmon, A. N. Yaresko, *Phys. Rev. B* **2003**, 68, 214424; d) A. N. Yaresko, V. N. Antonov, B. N. Harmon, *Phys. Rev. B* **2003**, 68, 214426.
- [16] B. T. Thole, G. van der Laan, *Phys. Rev. A* **1988**, 38, 1943.
- [17] G. van der Laan, B. T. Thole, *Phys. Rev. B* **1996**, 53, 14458; indeed, the value corresponds well to the $j-j$ or intermediate coupling scheme values (-6 and -5.34) for a $5f^1$ configuration, which however is incompatible with the chemical identity and magnetization data of **1**.
- [18] M. Colella, G. R. Lumpkin, Z. Zhang, E. C. Buck, K. L. Smith, *Phys. Chem. Miner.* **2005**, 32, 52.
- [19] P. Carra, B. T. Thole, M. Altarelli, X. Wang, *Phys. Rev. Lett.* **1993**, 70, 694.
- [20] B. T. Thole, P. Carra, F. Sette, G. van der Laan, *Phys. Rev. Lett.* **1992**, 68, 1943.
- [21] a) M. Finazzi, P. Sainctavit, A.-M. Dias, J.-P. Kappler, G. Krill, J.-P. Sanchez, P. Dalmas de Réotier, A. Yaouanc, A. Rogalev, J. Goulon, *Phys. Rev. B* **1997**, 55, 3010.
- [22] P.-Å. Malmqvist, B. O. Roos, *Chem. Phys. Lett.* **1989**, 155, 189.
- [23] a) C. Angeli, R. Cimiraglia, S. Evangelisti, T. Leininger, J.-P. Malrieu, *J. Chem. Phys.* **2001**, 114, 10252; b) C. Angeli, R. Cimiraglia, J.-P. Malrieu, *Chem. Phys. Lett.* **2001**, 350, 297.
- [24] a) I. B. Bersuker, *Chem. Rev.* **2013**, 113, 1351; b) I. B. Bersuker, *Chem. Rev.* **2001**, 101, 1067.
- [25] D. Ippolito, L. Martinelli, G. Bevilacqua, *Phys. Rev. B* **2005**, 71, 064419.
- [26] a) P. Delamoye, J. C. Krupa, S. Kern, C. K. Loong, G. H. Lander, *J. Less-Common Met.* **1986**, 122, 59; b) S. Kern, G. H. Lander, L. Soderholm, C.-K. Loong, F. Trouw, M. West, D. Hoisington, B. Cort, U. Welp, *J. Chem. Phys.* **1994**, 101, 9338; c) N. M. Edelstein, G. H. Lander in *The Chemistry of the Actinide and Transactinide Elements*, Vol. 4 (Eds.: L. R. Morss, N. M. Edelstein, J. Fuger), Springer, Dordrecht, **2008**, p. 2248.
- [27] K. S. Pedersen, D. N. Woodruff, S. K. Singh, A. Tressaud, E. Durand, M. Atanasov, P. Perlepe, K. Ollefs, F. Wilhelm, C. Mathonière, F. Neese, A. Rogalev, J. Bendix, R. Clérac, *Chem. Eur. J.* **2017**, 23, 11244.
- [28] CCDC 1533240 contains the supplementary crystallographic data for this paper. These data are provided free of charge by The Cambridge Crystallographic Data Centre.

Manuscript received: April 23, 2019

Revised manuscript received: June 14, 2019

Accepted manuscript online: July 10, 2017

Version of record online: August 7, 2019